

3 EFFECT OF INTERLAYER ANIONS ON [NiFe]-LDH NANOSHEET WATER OXIDATION ACTIVITY

Adapted from Hunter, B. M.; Hieringer, W.; Winkler, J. R.; Gray, H. B.; Müller, A. M. Effect of Interlayer Anions on [NiFe]-LDH Nanosheet Water Oxidation Activity. *Energy & Environmental Science* **2016**, *9*, 1734. DOI : 10.1039/C6EE00377J.

3.1. Summary

We synthesized nickel-iron layered double hydroxide ([NiFe]-LDH) nanosheets with different interlayer anions to probe their role in water oxidation catalysis. In alkaline electrolyte in ambient air, carbonate rapidly replaced other interlayer anions and catalytic activity was highest. Electrocatalytic water oxidation in virtually carbonate-free alkaline electrolyte revealed that activity was a function of anion basicity. Our [NiFe]-LDH nanosheets, prepared by pulsed laser ablation in liquids, were regenerated in carbonate-containing aqueous KOH. Anion binding motifs were assessed by x-ray photoelectron spectroscopy in combination with density functional theory calculations, suggesting that nitrite species bound to edge-site Fe in the precatalyst correlated with higher water oxidation activity.

3.2. Introduction

The global supply of sustainable fuels affects every aspect of human life. Electrocatalytic water splitting ($2\text{H}_2\text{O} \rightarrow 2\text{H}_2 + \text{O}_2$) is a promising approach towards transportable, carbon-neutral hydrogen fuel. The water oxidation half reaction is more demanding because it involves four electron and proton transfer steps,^{1,2} for which highly active, earth-abundant catalysts are needed.

Layered double hydroxides (LDHs), materials based on mineral structures readily found in nature, have been shown to be active for water oxidation.³⁻²² We recently reported that a [NiFe]-LDH nanomaterial synthesized by pulsed laser ablation in liquids (PLAL) is among the best water oxidation catalysts made of earth abundant elements.²⁰

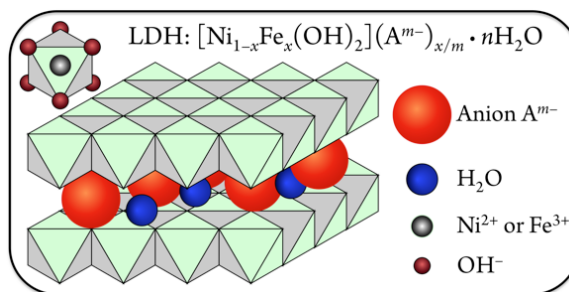


Figure 3.1. Schematic illustration of the [NiFe]-LDH structure. Anions and water are present in the interlayer space, and Ni^{2+} or Fe^{3+} ions are surrounded by six hydroxides in distorted octahedral coordination (upper left).

The structures of these nanosheet precatalysts were analyzed by x-ray diffraction (XRD) and Raman spectroscopy.²⁰ The [NiFe]-LDH materials consist of sheets of edge-shared nickel oxide octahedra, with varying amounts of ferric iron substituting at nickel sites. Hydroxide ligands extend into the interlayer space, which also contains water. The excess positive charges of Fe^{3+} substituting for Ni^{2+} are balanced by interlayer anions²³ (Figure 3.1).

The affinities for various mono- and divalent anions were established for [MgAl]-LDH hydrotalcite materials, which are structurally similar to our [NiFe]-LDHs. Data derived from anion-exchange isotherms revealed that divalent anions generally had higher ion selectivity than monovalent ones. The ion-exchange equilibrium constants followed the sequence $\text{CO}_3^{2-} > \text{SO}_4^{2-} > \text{OH}^- > \text{F}^- > \text{Cl}^- > \text{I}^-$.²⁴ Some hydroxide ions are likely always present in the interlayer galleries because OH^- partakes in strong interlamellar hydrogen bonding networks with the interlayer water, the ionic radius of hydroxide is very similar to that of water, and hydroxide is required to form the basic layers.²⁵ Moreover, given the large slab hydroxide and intercalated water content of LDHs, the experimental determination of minute amounts of interlayer OH^- ions is not practical. Nevertheless, we were interested in the identity of non-hydroxide interlayer anions in [NiFe]-LDHs during turnover in aqueous base in ambient air and their effects on water oxidation activity.

We exploited the benefits of PLAL as a synthetic method to investigate the role of interlayer anions in [NiFe]-LDH water oxidation catalysts. PLAL produces small, mono-

dispersed, surfactant-free nanoparticles.²⁶ The small size (<25 nm) allowed for the complete metathesis of interlayer anions simply by soaking in aqueous solutions. In addition, by modifying the anion content of the ablation liquid, we were able to synthesize species with different interlayer ions.

3.3. Experimental Section

3.3.1. Materials and Methods. Nanomaterial synthesis by pulsed laser ablation in liquids was performed in the Beckman Institute Laser Resource Center at California Institute of Technology. X-ray photoelectron spectroscopy was carried out at the Molecular Materials Research Center (Beckman Institute at California Institute of Technology).

All chemicals were used as received. Deionized water was obtained from a Barnstead Diamond Nanopure system and had a resistivity of $\geq 16 \text{ M}\Omega \text{ cm}^{-1}$. Data analysis and graphing was performed with Igor Pro 6.37 (Wavemetrics).

3.3.2. Synthesis. PLAL²⁶ was used to synthesize [NiFe]-LDH nanosheets.²⁰ Suspensions of 0.5 g iron (Alfa, -200 mesh) powder were stirred in 10 mL aqueous nickel salt solutions, using a magnetic stirrer in a 30 mL glass beaker at room temperature in ambient air. Metal salt solutions consisted of 3.0 M nickel nitrate ($\text{Ni}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$, Alfa), or 2.5 M nickel chloride ($\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$, JT Baker) and 0.5 M nickel nitrate, or 1.5 M each nickel sulfate ($\text{NiSO}_4 \cdot 6\text{H}_2\text{O}$, EMD) and nickel nitrate. The limited solubilities of nickel chloride and sulfate required addition of nickel nitrate to keep the total nickel concentration of all three solutions at 3.0 M. The material resulting from use of 3.0 M aqueous nickel nitrate solution is henceforward called [NiFe]-(NO_3^-)-LDH. Beakers and stir bars were thoroughly cleaned with *aqua regia* before use. A 355 nm, 8 ns pulse length, 90 mJ/pulse laser beam, provided by the third harmonic of a 10 Hz Q-switched Nd:YAG laser (Spectra-Physics Quanta-Ray PRO-Series), was focused 0.5 mm below the surface of the liquid with a 100 mm focal length plano-convex quartz lens. Each sample was irradiated for 60 min. After synthesis,

unreacted iron ablation target powder was separated from the nanoparticle suspensions using a rare-earth magnet. Solid nanopowders were obtained by centrifugation and washing with water until the supernatant did not show any nickel salt absorption. The nanoparticles were then washed twice with 3 mL acetone (EMD, OmniSolv®) and dried under vacuum.

Anion exchange was effected by suspending 10 mg [NiFe]-(NO₃⁻)-LDH nanosheets in 2 mL 1.0 M aqueous alkali salt solutions and letting the rigorously vortexed nanopowder soak for 45 min; the soaking time was 10 min for aqueous KOH solutions. The salts were K₂CO₃, KOH, KCl, NaF (all Mallinckrodt), Na₂SO₄ (EMD), NaClO₄ · 1H₂O (Fisher Scientific), KI, KBF₄, K₃PO₄, and K₂C₂O₄ · 1H₂O (all Sigma-Aldrich). For exchange as a function of solution pH, 1.5 mg [NiFe]-(NO₃)-LDH were dispersed in 1.0 mL 1.0 M (pH 14.0), 1.0 × 10⁻³ M (pH 11.0), or 1 × 10⁻⁶ M (pH 8.0) aqueous KOH solutions for 5 min. Anion-exchanged [NiFe]-LDH powders were obtained by centrifugation and washing first three times with 5 mL water and then twice with 3 mL acetone; the powders were dried under vacuum.

3.3.3. Physical Characterisation. X-ray photoelectron spectra (XPS) were collected using a Surface Science Instruments M-probe surface spectrometer. Monochromatic Al K α radiation (1486.6 eV) was used to excite electrons from the samples, which had either been deposited as dry powders on double-sided adhesive carbon tape (EM Sciences) or drop-cast from aqueous suspension on clean Cu foil and dried in ambient air at room temperature; we did not find different results for the two sample mounting methods. The sample chamber was maintained at <5 × 10⁻⁹ Torr. Survey scans from 0 to 1000 eV were performed to identify the elements present in the nanoparticles. Binding energies were referenced to the C 1s peak arising from adventitious carbon, taken to have a binding energy of 284.8 eV.²⁷ High-resolution spectra were collected for all materials for the Fe 2p, Ni 2p, C 1s, N 1s, and O 1s regions. In addition, depending on the elemental composition of the material, high-resolution spectra were taken in the Cl 2s, S 2s, I 3d, B 1s, F 1s, and P 2s regions. Quantitative peak areas were derived after Shirley background subtraction²⁸

and using relative sensitivity factors. Binding energies were obtained from the same peak fits. Quantitative XPS analysis was performed with CasaXPS (Version 2.3.16 PR 1.6).

XRD data were collected with a Bruker D2 PHASER diffractometer. Monochromatic Cu K α radiation (1.5418 Å; tube power 30 kV, 10 mA) was used; the instrument was equipped with 0.1° divergence, 1.5° Soller, and 0.6 mm detector slits, and had a 3-mm secondary anti-scatter screen. Diffracted radiation was collected with a Lynxeye detector. The instrument resolution was 0.030° in 2θ , and the counting time was 4.5 seconds per step, resulting in a total scan time of about 3.5 hours for each sample. Solid samples were deposited with vaseline (X-Alliance GmbH) on a zero-diffraction silicon plate (MTI Corporation). XRD background subtraction and Scherrer analysis²⁹ were performed with the Bruker DIFFRAC.SUITE software. Reflections were analyzed using a Scherrer constant K of 0.89 and integral breadth, defined as the total area under the diffraction maximum divided by the peak intensity.³⁰ Basal spacings d were derived using Bragg's law,³¹ $n\lambda = 2d \sin(\theta)$, where the integer n equals one, λ is the wavelength of the incident light, and θ is the angle of incidence. The (003) peaks of background-subtracted XRD data were fitted with Gaussians (ESI), whose centers at 2θ were divided by two to obtain the angle of incidence required to calculate basal spacings.

Attenuated total reflectance infrared (IR) spectra of dry nanoparticulate powders were collected with a Thermo Nicolet iS50 FT-IR spectrometer, equipped with a Pike Technologies GladiATR accessory plate, an uncooled pyroelectric deuterated triglycine sulfate (DTGS) detector, and a KBr beamsplitter. Spectra of the solid nanoparticulate powders were collected at room temperature in ambient air, and 132 scans were averaged for each sample.

3.3.4. Electrochemical Characterisation. Nanosheet powders were weighed with a high precision balance (Sartorius CPA225D), and aqueous 2 mg mL⁻¹ suspensions were prepared. A catalyst loading of 40 μ g was used throughout this work and was obtained by

drop-casting 20 μL of these suspensions on highly-ordered pyrolytic graphite (HOPG) disks, which were dried in ambient air under a heat lamp at 50°C . The electrode disk had stabilizing epoxy around its side and a surface area of 0.20 cm^2 . HOPG electrodes were cleaned by soaking for 5 min in concentrated hydrochloric acid, washed with water, and their surfaces were polished using 400 and 600 grit sandpaper, after which the graphite was cleaved with adhesive tape to obtain a fresh HOPG surface for each catalyst.

Measurements were carried out in ambient air or argon atmosphere in 100 mL three-neck round-bottom flasks, filled with 25 mL electrolyte. An Hg/HgO reference electrode (CH Instruments) and a Ni gauze (Alfa) counter electrode were used. All data were collected at room temperature, using a rotating disk electrode (RDE) setup at 1,500 rpm. Experiments in Ar atmosphere were carried out in a glove box, whose catalyst tolerates water; during oxygen evolution the catalyst was shut off, and after experiments the box was thoroughly flushed with Ar. In ambient air, a Pine MSR variable speed rotator and a Gamry Reference 600 potentiostat were used. In Ar atmosphere, a Pine WaveNow potentiostat and a (smaller) home-built RDE apparatus were employed; the rotation speed was determined to be 1,500 rpm with a laser tachometer.

In ambient air, the electrolyte was aqueous 1.0 M (pH 14.0) KOH. The electrolyte took up CO_2 from ambient air, which was dissolved as carbonate at this high pH. Even highest purity reagent grade alkali hydroxide solutions contain a minimum of 1% ($\sim 0.1\text{ M}$) alkali carbonate.³² Measurements in virtually carbonate-free electrolyte were performed under Ar atmosphere in a glove box. The electrolyte was prepared in the box from thoroughly degassed water, 1.0 M high purity KOH (Alfa, 99.98%, packaged under Ar), and 0.43 M barium hydroxide ($\text{Ba}(\text{OH})_2 \cdot \text{H}_2\text{O}$, Sigma-Aldrich). The barium hydroxide was added in excess to precipitate all dissolved carbonate as BaCO_3 , rendering the supernatant electrolyte virtually free of carbonate (see IR data below). Before use, an Hg/HgO reference electrode was equilibrated for one week in this solution. The pH of the virtually carbonate-free electrolyte was measured to be 14.6. Electrolyte from the same stock solution was used for all experiments requiring carbonate-free electrolyte.

Chronopotentiometry was performed for 3.5 hours at 1 mA cm^{-2} . Observed fluctuations in the data were due to formation and release of oxygen bubbles from the electrode surface. Cyclic voltammograms were measured at 0.1 V s^{-1} scan rate and after the working electrode had been held for 10 min at a current density of 1.0 mA cm^{-2} . The current density *versus* potential data were post-measurement corrected for uncompensated resistance losses (details are described elsewhere).²⁰ All polarization potentials reported here are relative to the normal hydrogen electrode (NHE), and current densities are per geometric area. Overpotentials η were calculated from polarization potentials E_p as $\eta = E_p - (1.23 \text{ V} - 0.059 \text{ V} \cdot \text{pH})$, taking into account the different pH values of electrolytes with and without carbonate.

3.3.5. Computational Methods. Density-functional theory calculations were performed with the Turbomole program package.³³ The PBE0 hybrid functional³⁴⁻³⁶ was used throughout this work. The SV(P) basis set³⁷ was employed for geometry optimizations as well as for N 1s core level energy calculations. Solvent screening effects were approximately included via the conductor-like screening model (COSMO)^{38, 39} with a solvent permittivity of 80. All calculations were spin-unrestricted. In this work, we imposed the lowest total spin projection $S_z = 0.5$ possible for the cluster models used in this work (one excess spin-up spin orbital in the Slater determinant). No point group symmetries were assumed. The model clusters were subjected to constrained geometry optimizations, where the atomic Ni, O, H positions of the parent LDH structure were kept fixed at the experimental positions, whereas the positions of all other atoms (Fe, additional OH groups, nitrate/nitrite anions) were optimized. Standard convergence criteria (Turbomole defaults) were used in general. Only for the calculation of the core-level binding energies, SCF convergence criteria were tightened to 10^{-7} a. u. for the energy and density matrix.

The calculation of N 1s core-level binding energies (BEs) was performed using N 1s orbital energies and with the so-called Slater transition state (STS) method.⁴⁰ Initial state contributions to core level shifts (is-CLS) were estimated as orbital energy differences of

the N 1s orbital energies ε in the chosen SCF solutions of the clusters without any core hole. Only *shifts* in core-level binding energies (core-level shifts, CLS) were relevant in this work, absolute binding energies should not be compared to experimental XPS data.

3.4. Results and Discussion

We synthesized twelve materials with different interlayer anions, either by anion exchange from nitrate-based [NiFe]-LDH nanosheets made by PLAL from nitrate-containing ablation liquid,²⁰ denoted [NiFe]-(NO₃⁻)-LDH, or with Cl⁻ or SO₄²⁻ in the PLAL ablation liquid. Aqueous solutions for anion exchange contained 1.0 M BF₄⁻, Cl⁻, ClO₄⁻, CO₃²⁻, C₂O₄²⁻, F⁻, I⁻, PO₄³⁻, or SO₄²⁻.

We discovered that all interlayer anions quickly exchanged for carbonate in 1.0 M aqueous KOH in ambient air, as evidenced by IR, XPS, and XRD data (see below). Strongly alkaline aqueous electrolyte exposed to ambient air is self-buffered regarding carbonate content, as dissolved carbonate is in steady-state equilibrium with gaseous CO₂.⁴¹ The active catalyst was therefore the carbonate-containing species, regardless of the precatalyst composition.

3.4.1. Physical Characterization of Materials

3.4.1.1. X-Ray photoelectron spectra. We collected XPS data to identify nanoparticle compositions by peak integrations of high-resolution spectra of the Ni 2p, Fe 2p, B 1s, C 1s, N 1s, O 1s, F 1s, Cl 2s, I 3d, P 2s, and S 2s regions, where applicable. The regions were chosen as to collect data on transitions with the highest x-ray ionization cross-sections,⁴² and the data were background-subtracted.²⁸ We deliberately did not attempt to quantify oxygen content from XPS data because its amounts are regularly overestimated; oxygen occurs in many adventitious sources.

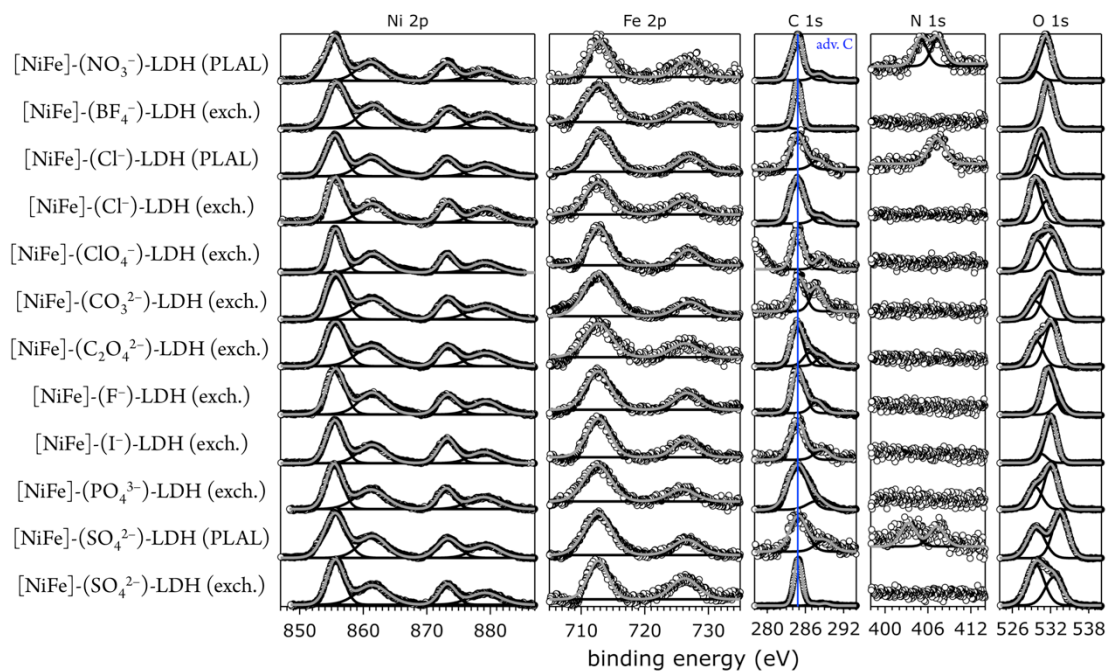


Figure 3.2. XPS data of [NiFe]-LDH nanosheets with different interlayer anions as synthesized in the Ni 2p, Fe 2p, C 1s, N 1s, and O 1s regions. The materials were prepared by pulsed-laser ablation in liquids (PLAL) or by anion exchange from [NiFe]-(NO₃⁻)-LDH (exch.). Open circles, data; black lines, peak fits; grey lines, envelopes. The blue line in the C 1s panel indicates the binding of adventitious carbon.

The Ni 2p core-level binding energies of all catalysts were consistent with assignment to hydrated Ni(OH)₂,⁴³ with Ni 2p_{3/2} binding energies close to 855.5 eV. After exposure to 1.0 M aqueous KOH in ambient air, all [NiFe]-LDH materials featured an additional, lower binding-energy peak in the Ni 2p_{3/2} core level region, consistent with NiO.^{44, 45} The Fe 2p core level spectra of all catalysts showed peaks attributable to iron oxides and oxyhydroxides,^{13, 46} with Fe 2p_{3/2} binding energies close to 711.9 eV. Various iron oxides and oxyhydroxides, such as FeO, Fe₂O₃, Fe₃O₄, and FeOOH, have similar Fe core-level binding energies and spectral shapes.⁴⁶ Therefore, it is impossible to distinguish different Fe phases in our materials from Fe 2p XPS data. All materials contained 22% Fe relative to the total metal content.

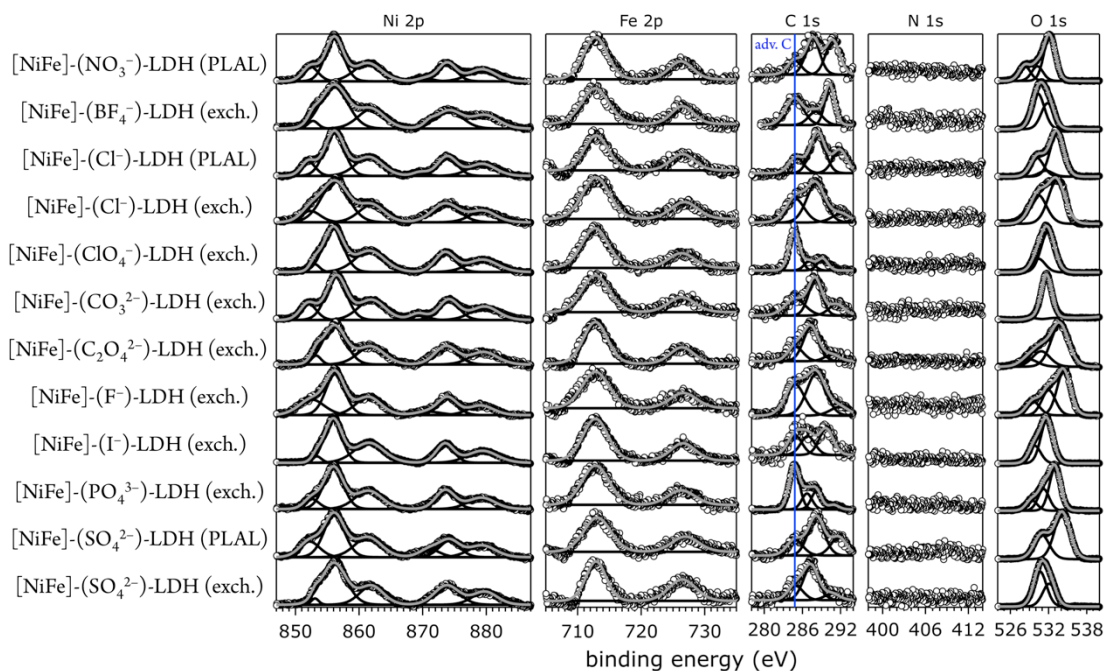


Figure 3.3. XPS data of [NiFe]-LDH nanosheets with different interlayer anions after suspension in 1.0 M aqueous KOH in ambient air in the Ni 2p, Fe 2p, C 1s, N 1s, and O 1s regions. The materials were prepared by pulsed-laser ablation in liquids (PLAL) or by anion exchange from [NiFe]-(NO₃⁻)-LDH (exch.). Open circles, data; black lines, peak fits; grey lines, envelopes. The blue line in the C 1s panel indicates the binding energy of adventitious carbon.

The N 1s core level spectra of [NiFe]-(NO₃⁻)-LDH, [NiFe]-(Cl⁻)-LDH made by PLAL and [NiFe]-(SO₄²⁻)-LDH made by PLAL showed peaks with binding energies around 407.3 eV, consistent with nitrate.⁴⁷ In addition, [NiFe]-(SO₄²⁻)-LDH made by PLAL exhibited an N 1s peak at 403.5 eV, attributable to nitrite.⁴⁸ As reported by us before, PLAL-synthesized [NiFe]-(NO₃⁻)-LDH featured in addition to the nitrate signal an N 1s peak centered at 405.1 eV.²⁰ After exposure to 1.0 M aqueous KOH in ambient air, we could no longer detect any peaks in the N 1s core level region, indicating that all nitrogen species were readily exchanged by other anions. The O 1s spectra were consistent with Fe or Ni oxide and hydroxide species.⁴⁴ Contributions attributable to oxygen-containing anions⁴⁴ and from adventitious sources were also present. The C 1s spectra of as-synthesized [NiFe]-LDH materials with different interlayer anions showed mostly the presence of adventitious carbon, whereas those of nanosheets that had been exposed to 1.0

M aqueous KOH in ambient air exhibited additional peaks, which were consistent with more highly oxidized carbon.⁴⁴ High-resolution XP spectra of anionic hetero-atoms (other than Ni, Fe, C, N, or O) showed that the initially present anions were lost after exposure to pH 14 aqueous KOH solution in ambient air (Figure 3.4). Quantification of non-metal atom content in the as-synthesized [NiFe]-LDH materials is summarized in Table 3-1. Additional hydroxide ions may have been present to balance the overall charge in the materials.

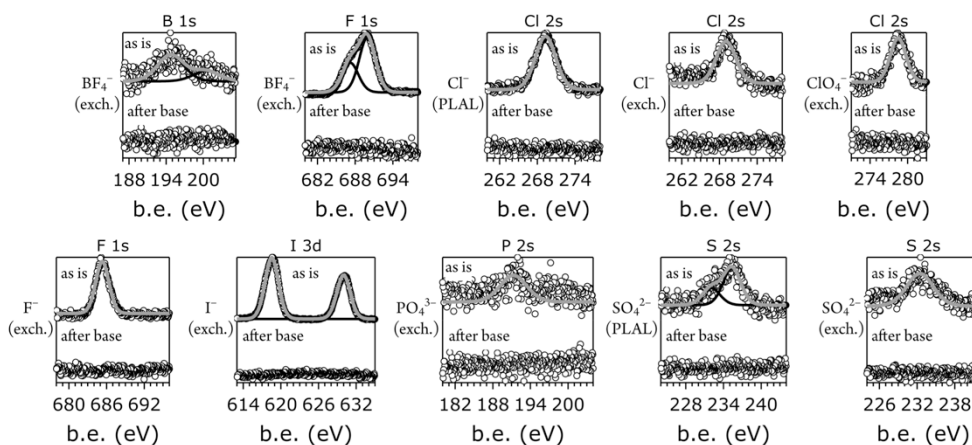


Figure 3.4. XPS data of [NiFe]-LDH nanosheets with different interlayer anions as synthesized (as is) and after suspension in 1.0 M aqueous KOH in ambient air (after base) in the B 1s, F 1s, Cl 2s, I 3d, P 2s, and S 2s regions, where applicable; b.e., binding energy. Open circles, data; black lines, peak fits; grey lines, envelopes.

Table 3-1: Summary of XPS data analysis of [NiFe]-(A^{m-})-LDH materials with different interlayer anions A^{m-} , prepared by pulsed-laser ablation in liquids (PLAL) or by anion exchange from [NiFe]-(NO_3^-)-LDH (exch.). Portion of anion elements with respect to total metal content; the relative error is $\pm 10\%$.

Material	XPS line	% Non-metal atoms
[NiFe]-(NO_3^-)-LDH (PLAL)	N 1s	10
[NiFe]-(BF_4^-)-LDH (exch.)	B 1s	18
	F 1s	72
[NiFe]-(Cl^-)-LDH (PLAL)	Cl 2s	16
	N 1s	4.7
[NiFe]-(Cl^-)-LDH (exch.)	Cl 2s	21
[NiFe]-(ClO_4^-)-LDH (exch.)	Cl 2s	10
[NiFe]-(CO_3^{2-})-LDH (exch.)	C 1s	20
[NiFe]-($\text{C}_2\text{O}_4^{2-}$)-LDH (exch.)	C 1s	20
[NiFe]-(F^-)-LDH (exch.)	F 1s	18
[NiFe]-(I^-)-LDH (exch.)	I 3d	19
[NiFe]-(PO_4^{3-})-LDH (exch.)	P 2s	8.0
[NiFe]-(SO_4^{2-})-LDH (PLAL)	S 2s	10
	N 1s	4.2
[NiFe]-(SO_4^{2-})-LDH (exch.)	S 2s	17

Knowing that all nitrogen species of the as-synthesized [NiFe]-(NO₃⁻)-LDH nanosheets were replaced by carbonate in strong aqueous base in ambient air, we exposed [NiFe]-(NO₃⁻)-LDH to aqueous KOH solutions with pH values of 8.0, 11.0, and 14.0 and took XP spectra (Figure 3.5). For comparison, we also collected XP spectra of commercial Ni(NO₃)₂ · 6H₂O, whose N 1s region featured a single peak centered at 407.4 eV, consistent with previous reports for metal nitrate.⁴⁸ The observed C 1s signal for Ni(NO₃)₂ · 6H₂O was attributable to adventitious carbon, and the O 1s peak was consistent with a transition metal nitrate.⁴⁴ Its Ni 2p_{3/2} peak was centered at 857.0 eV as expected,⁴⁴ and no peaks in the Fe 2p core level region were observed.

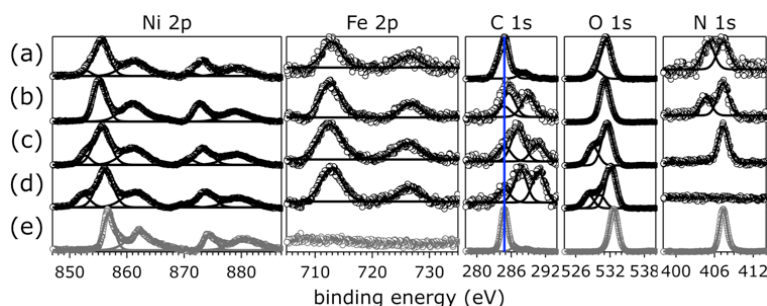


Figure 3.5. XPS data of [NiFe]-(NO₃⁻)-LDH (as synthesized, a) and exchanged in different pH aqueous KOH solutions (b, pH 8.0; c, pH 11.0; d, pH 14.0). Depicted in grey are data of commercial Ni(NO₃)₂ · 6H₂O (e). The blue line in the C 1s panel indicates the binding energy of adventitious carbon. Open circles, data; lines, peak fits.

We found that all nitrogen species of the original material were gradually exchanged into carbon species with higher C 1s binding energy than adventitious carbon. As the solution pH rose, the N 1s peak centered at 405.1 eV disappeared before that at 407.3 eV. After exposure to pH 14.0 solution in ambient air, no nitrogen species were detectable (Figure 3.5). Instead the material took up carbonate from the aqueous base (see also IR spectra below). Quantification of XPS signals as a function of solution pH showed a linear decline of N 1s and a concomitant increase of C 1s signals (Figure 3.6). In aqueous KOH solutions at room temperature with pH values above 10, the predominant species resulting from dissolution of ambient CO₂ is carbonate, whereas at pH 8.0 dissolved inorganic carbon speciation favors HCO₃⁻ over CO₃²⁻ ions.⁴¹ The observed C 1s signals of

[NiFe]-LDH materials after exposure to different pH aqueous KOH solutions were consistent with transition metal bicarbonates and carbonates.⁴⁴

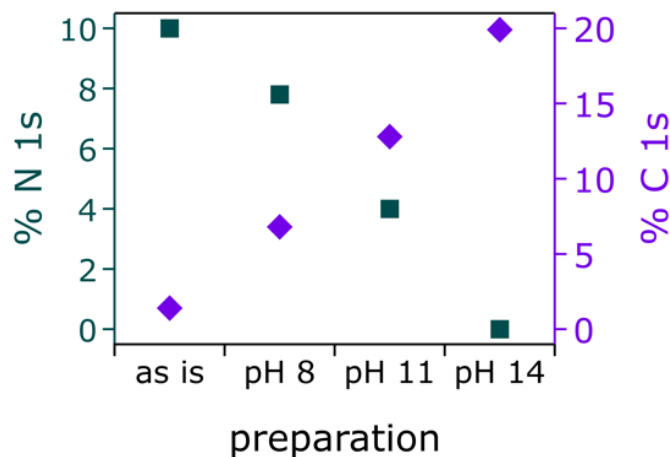


Figure 3.6. Quantification of the N 1s (teal) and C 1s (purple) regions of [NiFe]-(NO₃)⁻-LDH (as is) and exchanged in different pH aqueous KOH solutions in percent with respect to the total metal content.

3.4.1.2. X-Ray diffraction data. XRD data were collected to determine crystalline phases, basal spacings by Bragg's law³¹ analysis, and crystallite sizes by Scherrer analysis.²⁹ XRD data of [NiFe]-LDH nanosheets with different interlayer anions as synthesized (as is) and after suspension in 1.0 M aqueous KOH in ambient air are depicted in Figure 3.7.

All materials showed XRD patterns characteristic for layered double hydroxides.²³ The intensities of the basal (00*l*) reflections decrease as *l* increases. The intensity ratio of the (006) and (003) reflections is a measure of the interlamellar electron density. Loss of water in the interlayer galleries, associated with reduction in interlamellar electron density, has been reported to lead to less intense (006) reflections with respect to (003) diffractions.⁴⁹

All XRD peaks were significantly broadened, owing to small crystallite size and stacking faults. The XRD data of [NiFe]-(ClO₄⁻)-LDH (exch., as synthesized) and [NiFe]-(SO₄²⁻)-LDH (PLAL, as synthesized) materials showed non-uniform ("saw-tooth")

broadening of ($h0l$) reflections, which are indicative of turbostratic disorder.²⁵ The observed reflections were indexed in a three-layer **3R** polytype with rhombohedral symmetry, such as in synthetic hydrotalcite⁵⁰ (Figure 3.8).

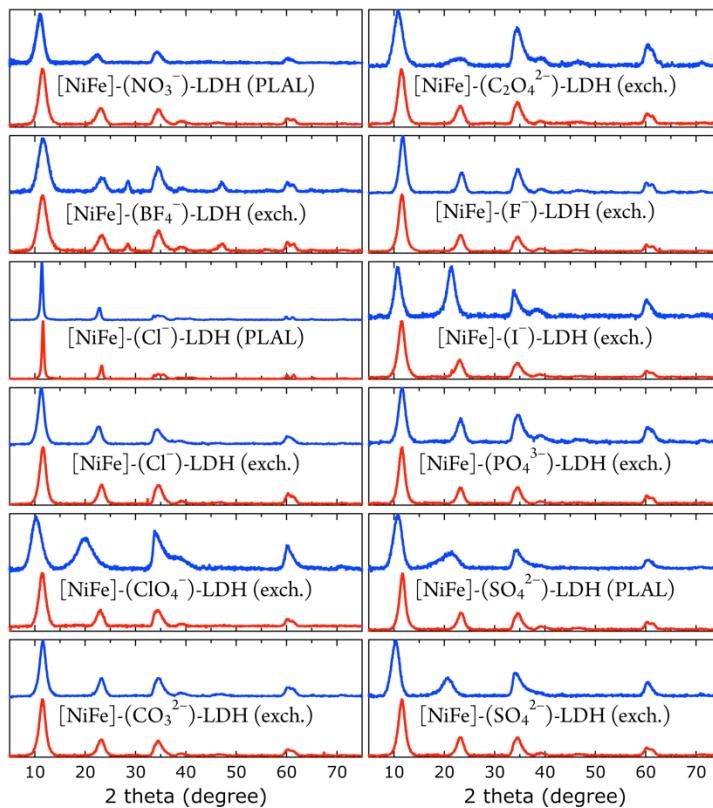


Figure 3.7. XRD data of [NiFe]-LDH nanosheets with different interlayer anions as synthesized (blue) and after suspension in 1.0 M aqueous KOH in ambient air (red).

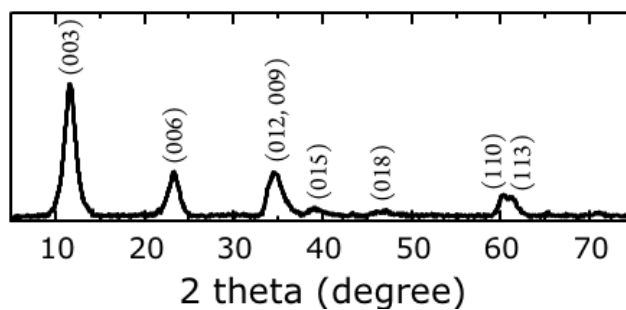


Figure 3.8. XRD data of [NiFe]-(CO₃²⁻)-LDH nanosheets with indices of reflection.

Table 3-2: Crystalline domain sizes from Scherrer analysis of [NiFe]-(A^{m-})-LDH materials with different intercalated anions A^{m-} , prepared by PLAL or by anion exchange from [NiFe]-(NO_3^-)-LDH (exch.), as synthesized and after exposure to 1.0 M aqueous KOH. The error in all dimensions is $\pm 13\%$.

A^{m-} (prep.)	thickness (nm) as synth.	thickness (nm) after base	diameter (nm) as synth.	diameter (nm) after base
NO_3^- (PLAL)	4	4.4	13	13
BF_4^- (exch.)	3.9	3.9	14	12
Cl^- (PLAL)	12	13	21	23
Cl^- (exch.)	4.8	4.7	13	14
ClO_4^- (exch.)	3.2	4.5	12	12
CO_3^{2-} (exch.)	4.8	4.6	12	13
$\text{C}_2\text{O}_4^{2-}$ (exch.)	3.6	4.6	10	13
F^- (exch.)	3.9	4.7	11	14
I^- (exch.)	4.7	4.5	12	13
PO_4^{3-} (exch.)	4.5	4.8	11	14
SO_4^{2-} (PLAL)	3.8	5.2	12	14
SO_4^{2-} (exch.)	3.8	4.7	10	13

We obtained crystallite sizes from Scherrer analysis²⁹ of our XRD data (Table 3-2). Crystalline domain sizes in the a and c unit cell directions were derived from broadening of the (110) and (00 l) ($l = 3, 6$) reflections, respectively.²⁵ In case of [NiFe]-(ClO_4^-)-LDH (exch., as synthesized) and [NiFe]-(SO_4^{2-})-LDH (PLAL, as synthesized) materials, only (003) reflections were used to determine nanosheet thicknesses, as the asymmetric line shape of the (006) reflections hampered proper analysis. The unit cell directions a and c correspond to lateral size (diameter) and nanosheet thickness, respectively. Most materials had very similar size. However, the [NiFe]-(Cl^-)-LDH (PLAL) materials, both as synthesized and after suspension in 1.0 M aqueous KOH in ambient air, exhibited significantly narrower peaks, indicating larger crystallite sizes.

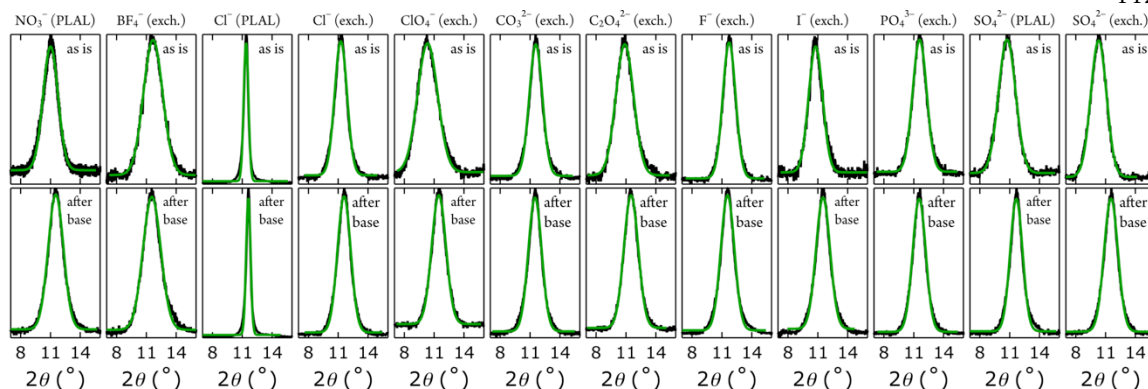


Figure 3.9. Gaussian fits (green) of the (001) peaks (black) of XRD data of [NiFe]-LDH nanosheets with different interlayer anions.

Gaussian fits of the (003) peaks (Figure 3.9) were performed to obtain the angle of incidence required to calculate basal spacings. The fits had an average error in 2θ of $\pm 0.05^\circ$, resulting in a basal spacing error of $\pm 0.03 \text{ \AA}$. The derived basal spacings of [NiFe]-(A^{m-})-LDH materials with different intercalated anions A^{m-} , prepared by PLAL or by anion exchange from [NiFe]-(NO_3^-)-LDH (exch.), are depicted in Figure 3.10.

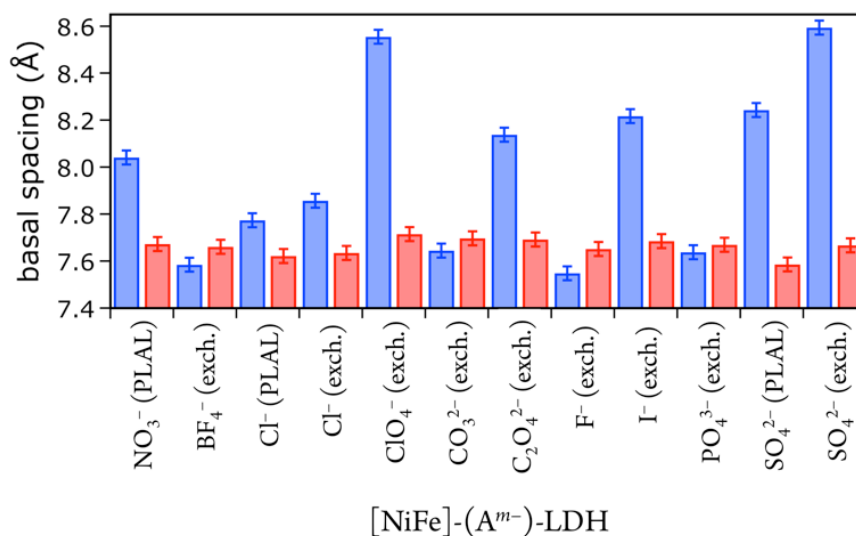


Figure 3.10. Basal spacings of [NiFe]-LDH nanosheets with different interlayer anions as synthesized (blue) and after suspension in 1.0 M aqueous KOH in ambient air (red).

We correlated the basal spacings of [NiFe]-LDH materials with the ionic radii of the anions. Non-spherical anions occupy interlamellar galleries of LDH materials at various angles, and their arrangement depends on many factors.^{24,25,51} Therefore, we limited our analysis to the spherical halogen anions. We found a linear correlation of measured basal spacing with anionic radii. Our observation indicates that the anions did indeed reside in the interlayer galleries of our LDH materials.

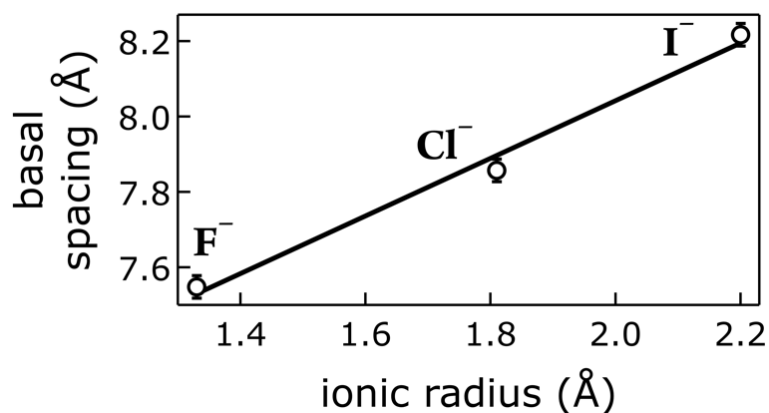


Figure 3.11. Correlation of ionic radii⁵² of intercalated halogen anions A^{m-} with basal spacings of [NiFe]-(A^{m-})-LDH materials.

3.4.1.3. Infrared data. IR spectra were collected to shed more light on the identity of interlayer anions in our [NiFe]-LDH water oxidation catalysts. Layered double hydroxides have a huge affinity towards carbonate incorporation.^{53,54} Given the ubiquitous presence of carbonate in aqueous base in ambient air, spectroscopic evidence for virtually carbonate-free materials is paramount. The IR bands in the 1200–1600 cm^{-1} region are characteristic for alkali carbonate (one narrow peak at 1400 cm^{-1}) or nitrate (two broader bands centered around 1400 cm^{-1}).⁵⁵

Our [NiFe]-(NO_3^-)-LDH nanosheets turned into [NiFe]-(CO_3^{2-})-LDH materials in strong aqueous base in ambient air (Figure 3.12). We confirmed the identity of interlayer carbonate by collecting IR data after soaking [NiFe]-(NO_3^-)-LDH in 0.1 M aqueous K_2CO_3 solution.

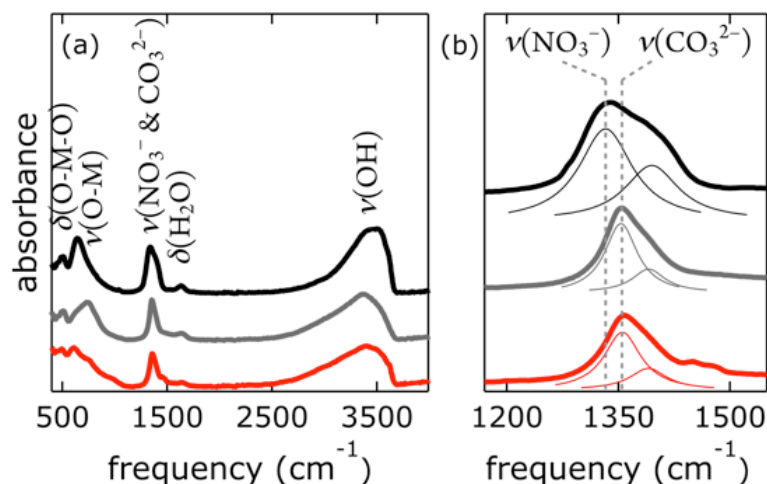


Figure 3.12. Infrared spectra of [NiFe]-(NO₃⁻)-LDH nanosheets as synthesized (black), after being suspended in 0.1 M aqueous K₂CO₃ solution (grey), and after being suspended in 0.1 M aqueous KOH (red); (a) full spectra, (b) magnification of the region characteristic for NO₃⁻ and CO₃²⁻, Lorentzian fits are depicted as thin lines.

One way of de-carbonation is precipitation of dissolved carbonate with Ba²⁺ as BaCO₃.⁵⁶ We used this method in inert atmosphere (Figure 3.13), using Ba(OH)₂, as to not introduce anions other than hydroxide. All attempts to achieve carbonate-free electrolyte in ambient air failed (Figure 3.13). Virtually carbonate-free electrolyte was prepared under Ar as described above. In the glove box, we dispersed [NiFe]-(NO₃⁻)-LDH in this electrolyte, let it settle overnight, and removed the supernatant. Still in Ar atmosphere, we dispersed the resulting material in water, let it settle overnight, removed the supernatant, and repeated this procedure twice. After the last supernatant removal, we let the material dry in the glove box. The IR spectrum (Figure 3.14) of this material clearly shows the characteristic redshift and broadening of the nitrate with respect to the carbonate band, indicating that we succeeded to exclude carbonate from our [NiFe]-(NO₃⁻)-LDH and electrolyte in the glove box.

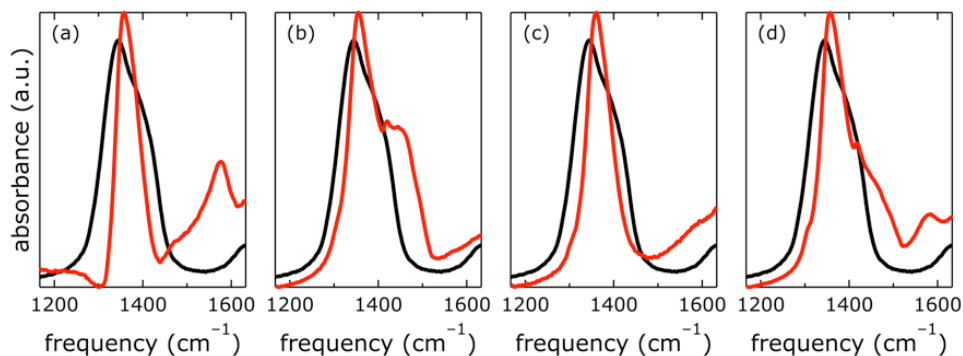


Figure 3.13. Infrared spectra of $[\text{NiFe}]-(\text{NO}_3^-)$ -LDH nanosheets as synthesized (black) and after being suspended in 0.1 M aqueous KOH (red). The red spectra were taken using different suspension solution conditions: (a), in ambient air, no $\text{Ba}(\text{OH})_2$; (b), in ambient air, with $\text{Ba}(\text{OH})_2$; (c), in glove box, no $\text{Ba}(\text{OH})_2$; (d), in glove box, with $\text{Ba}(\text{OH})_2$. All samples were subsequently worked up in ambient air.

The nitrate peak in the infrared spectrum of the as-synthesized $[\text{NiFe}]-(\text{NO}_3^-)$ -LDH nanosheets was broader than that observed for the $[\text{NiFe}]-(\text{NO}_3^-)$ -LDH nanosheets which had been soaked in carbonate-free aqueous base. We attributed this to a change in the morphology of the material at high pH. This is in agreement with the dramatic changes observed in the OH and Ni—O lattice regions upon exposure to highly alkaline solutions.

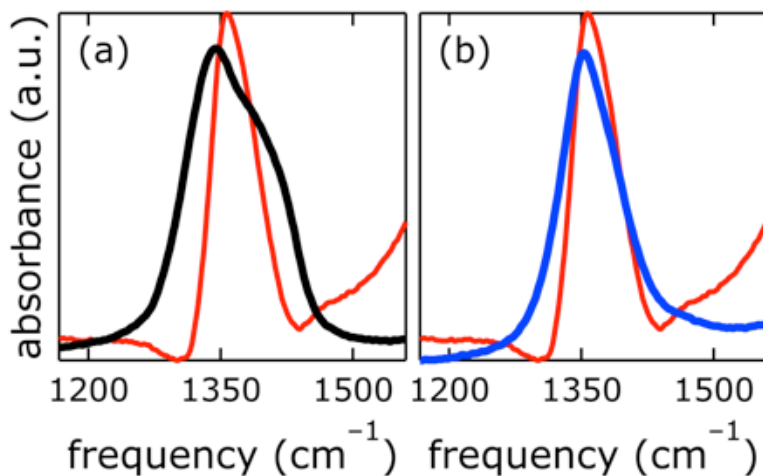


Figure 3.14. Infrared spectra of $[\text{NiFe}]-(\text{NO}_3^-)$ -LDH nanosheets as synthesized (black), after being suspended in carbonate-free strong base electrolyte in Ar atmosphere as described above (blue), and after being suspended in 0.1 M aqueous KOH in ambient air (red).

3.4.1.4 Electrochemical Characterization. We prepared 1.0 M aqueous KOH electrolyte in a virtually CO₂-free atmosphere (glove box) and scrubbed the solution of any residual dissolved carbonate by saturating with barium hydroxide. IR data confirmed that the [NiFe]-LDH catalysts did not take up carbonate under these conditions (see above). Constant current electrolysis was used to assess long-term water oxidation activity; measured potentials were converted to overpotentials η to facilitate comparison between electrolytes with and virtually without carbonate. In Figure 3.15, the overpotentials as a function of time are shown for [NiFe]-(NO₃⁻)-LDH in alkaline electrolytes with and without carbonate. The [NiFe]-(CO₃²⁻)-LDH catalyst performed better than the [NiFe]-(NO₃⁻)-LDH, indicating that interlayer anions matter during water oxidation catalysis.

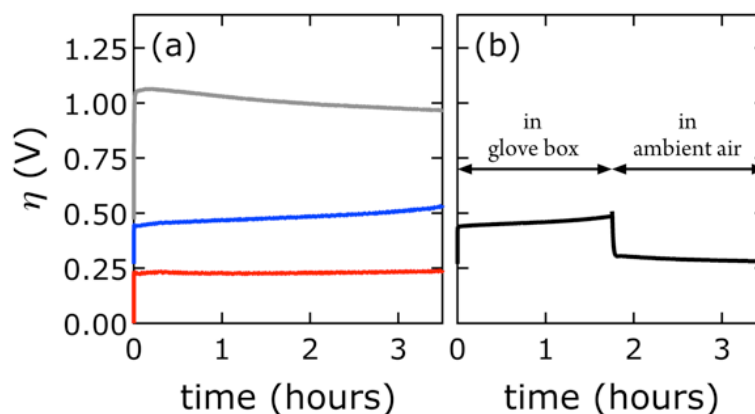


Figure 3.15. Constant current electrolysis of [NiFe]-(NO₃⁻)-LDH (PLAL) at 1 mA cm⁻². Measured applied potentials were converted to overpotentials η to account for the different pH values of alkaline electrolytes with and virtually without carbonate. (a) Synthesized nanosheets were exposed to only one electrolyte: virtually carbonate free (glove box, blue), with carbonate (ambient air, red). The grey curve corresponds to the bare graphite electrode. (b) [NiFe]-(NO₃⁻)-LDH electrode was first anodically polarized in virtually carbonate-free electrolyte (glove box), then brought into ambient air and further polarized in electrolyte with carbonate.

Interestingly, after water oxidation catalysis with [NiFe]-(NO₃⁻)-LDH catalyst in virtually carbonate-free alkaline electrolyte, most of the activity of the material recovered when the electrode was removed from the glove box, and the electrolysis was continued in aqueous base in ambient air (Figure 3.15b). Enhanced catalytic activity was observed

instantaneously as [NiFe]-(CO₃²⁻)-LDH was formed. The [NiFe]-LDH nanosheets were regenerated in aqueous base in ambient air, and high activity was detected even after initial catalytic turnover without any carbonate (3.15b). Differences in electrochemical response of the bare graphite electrode in carbonate-free and carbonate-containing electrolytes were insignificant (Figure 3.16).

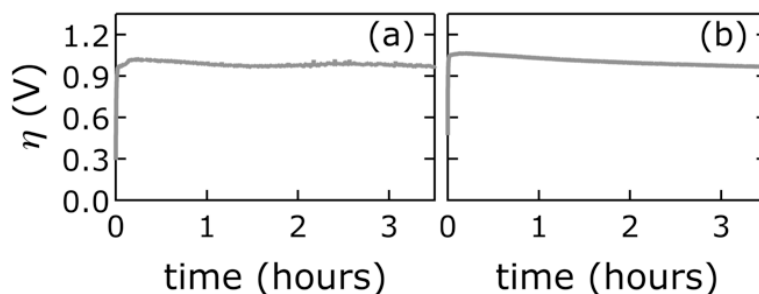


Figure 3.16. Constant current voltammograms of bare graphite electrodes in carbonate-containing (a) and virtually carbonate-free (b) electrolytes.

We probed all twelve materials in a virtually carbonate-free alkaline electrolyte to assess the effects of different interlayer anions (other than hydroxide) in the precatalysts on water oxidation catalysis. We obtained overpotential values at 1 mA cm⁻² current density after 10 min of catalytic turnover. At the chosen current density most catalysts exhibited appreciable stability under anodic polarization. We compared activities in carbonate-free and carbonate-containing alkaline electrolytes. In all cases, catalytic activity in aqueous base in ambient air was superior (Figure 3.18).

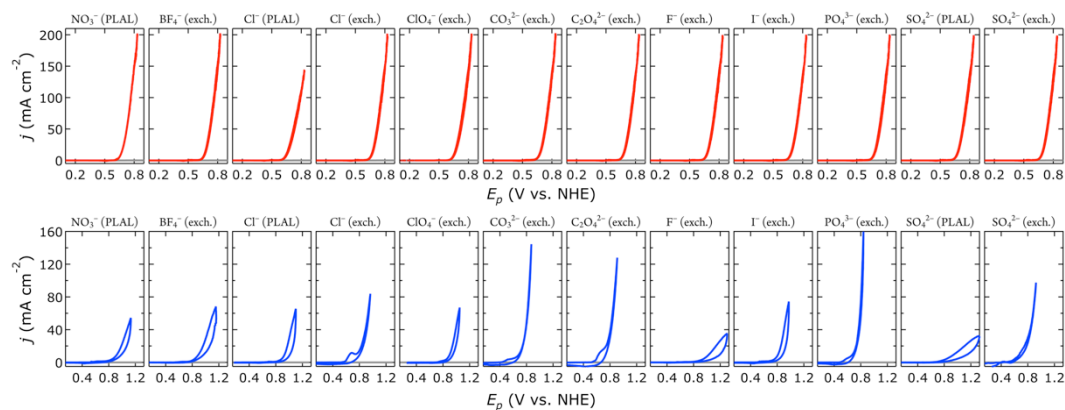


Figure 3.17. Cyclic voltammograms of [NiFe]-LDH materials with different interlayer anions in virtually carbonate-free electrolyte in a glove box (blue) and after suspension in 1.0 M aqueous KOH in ambient air (red). Cyclic voltammetry data of bare HOPG are shown in grey.

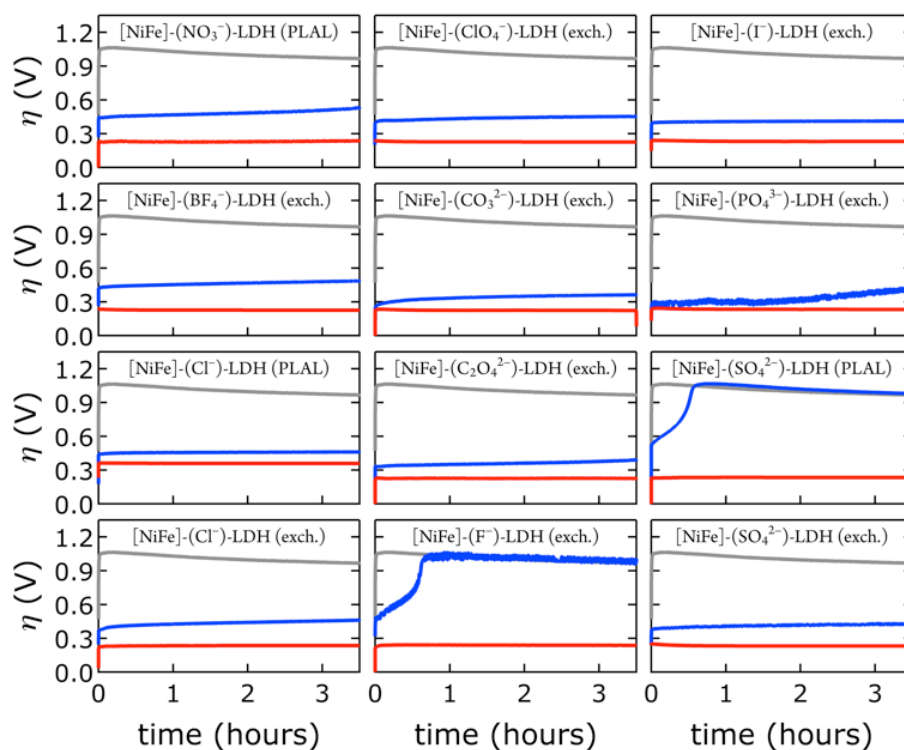


Figure 3.18. Constant current electrolysis of [NiFe]-LDH materials with different interlayer anions in virtually carbonate-free electrolyte in a glove box (blue) and after suspension in 1.0 M aqueous KOH in ambient air (red). Chronopotentiometry data of bare HOPG are shown in grey. All data were collected at a constant current density of 1 mA cm^{-2} .

After exposure to carbonate-containing electrolyte (1.0 M aqueous KOH in ambient air), all materials immediately featured low, very similar overpotentials, consistent with formation of [NiFe]-(CO₃²⁻)-LDH materials; only the [NiFe]-(Cl⁻)-LDH material synthesized by PLAL, which consisted of larger nanosheets (see Table 3-2), exhibited slightly inferior performance. Likewise, the cyclic voltammograms of all materials after exposure to 1.0 M aqueous KOH in ambient air were very similar; again, the [NiFe]-(Cl⁻)-LDH synthesized by PLAL showed slightly less current density (Figure 3.17). All materials exhibited remarkable stability over several hours in carbonate-containing (self-buffered) alkaline electrolyte.

3.4.2. Data Correlations

We tried to find correlations of electrochemical data, such as overpotentials and prewave peak positions, with the materials' structural and chemical characteristics, such as basal spacing, intrasheet [NiFe](OH)₂ structure, and interlayer anion basicity. Data of unstable materials, such as [NiFe]-(F⁻)-LDH (exch.) and [NiFe]-(SO₄²⁻)-LDH (PLAL), were not included into correlations. Only small amounts of the initially deposited [NiFe]-(F⁻)-LDH (exch.) and [NiFe]-(SO₄²⁻)-LDH (PLAL) materials were visible on the HOPG electrode after chronopotentiometry experiments.

We derived overpotentials of [NiFe]-LDH materials with different interlayer anions from chronopotentiometry data, which were collected in virtually carbonate-free electrolyte (glove box). They are plotted as a function of the pK_a values of the conjugate acids of the interlayer anions (Table 3-3) in Figure 3.19.

Table 3-3: Anions, conjugate acids, and pK_a values of conjugate acids of anions with references.

Anion	Conjugate acid	pK_a	Reference
NO_3^-	HNO_3	-1.3	59
BF_4^-	HBF_4	-0.44	60
Cl^-	HCl	-9.3	61
ClO_4^-	HClO_4	1.77	62
CO_3^{2-}	HCO_3^-	10.25	62
$\text{C}_2\text{O}_4^{2-}$	HC_2O_4^-	4.19	62
F^-	HF	3.45	62
I^-	HI	0.77	62
PO_4^{3-}	HPO_4^{2-}	12.67	62
SO_4^{2-}	HSO_4^-	1.92	62

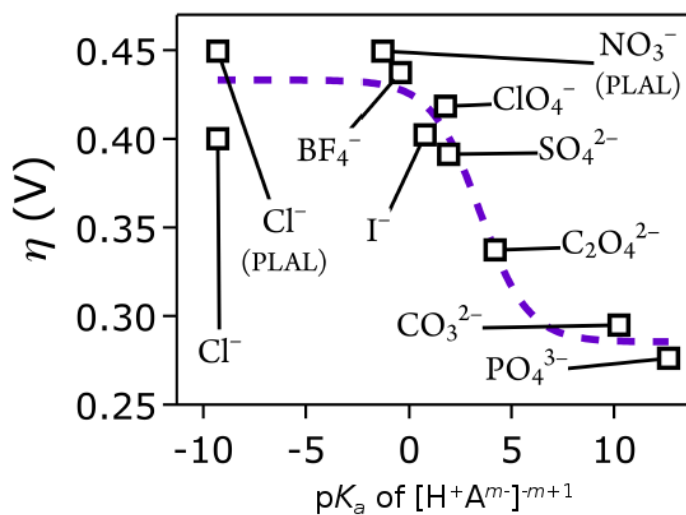


Figure 3.19. Overpotentials η of [NiFe]-LDH materials with different interlayer anions A^{m-} derived from constant current electrolysis at 1 mA cm^{-2} in virtually carbonate-free electrolyte as a function of anion basicity. Bare anion labels denote materials prepared by exchange from [NiFe]-(NO_3)-LDH.

We discovered a strong correlation between water oxidation activity and the pK_a values of the conjugate acids of the interlayer anions; there is sigmoidal behavior with a midpoint of 3.4 ± 0.7 (Figure 3.19).

Mechanistically, this behavior suggests a base-assisted deprotonation step during turnover. The apparent pK_a , determined electrochemically, may be related to the pK_a of a higher-valent metal-oxo species, which is typically much lower than 7. This effect manifests as an “oxo wall” between the Fe and Co triads of the periodic table.⁵⁷ Transition metals to the left of the wall make stable oxo complexes, whereas those to the right are too basic and are easily attacked by electrophiles. Different Lewis basicities, which would lower the potential required to reach the necessary Fe and/or Ni oxidation states, could also be at play.

Our discovery of the sigmoidal dependence of water oxidation activity on anion basicity is perhaps surprising, given that there is 1 M OH^- in the electrolyte. Hydroxide is of course also a good base. It is unclear, however, how much hydroxide resides in the interlayer galleries. Our results imply that the di- and tri-valent anions outcompeted hydroxide presence in the interlayer space. This is consistent with previous reports on anion affinities in LDHs (see above).²⁴ Our observation that the $[\text{NiFe}](\text{CO}_3^{2-})\text{-LDH}$ catalyst regenerated in carbonate-containing aqueous base and showed exceptional robustness supports our conclusion that this higher-valent anion was strongly bound and played an active role during turnover. We cannot exclude that in the regime of lower activity, where we have monovalent interlayer anions (to the left in Figure 3.19), the catalysis is governed by hydroxide-mediated deprotonation. It is important to note, however, that catalytic activity can be enhanced by di- and tri-valent anions. The higher charge of multivalent anions makes them stronger proton acceptors and electron donors than monovalent anions. It is possible that a strongly bound proton acceptor is required to reduce the activation barrier for water oxidation.

We tried to correlate Ni-based redox features to interlayer anion basicity to assess if more electron-rich anions would lead to electronic changes in the nickel hydroxide layers. We deliberately chose the reduction wave of the cyclic voltammograms for analysis as the

oxidation prewave was partly obscured by the catalytic wave, rendering an accurate determination of the peak maximum problematic. This is illustrated in Figure 3.20 (a). We did not observe a clear correlation of the central polarization potential of the reduction waves of [NiFe]-LDH nanosheets with interlayer anions exhibiting different basicities or overpotential.

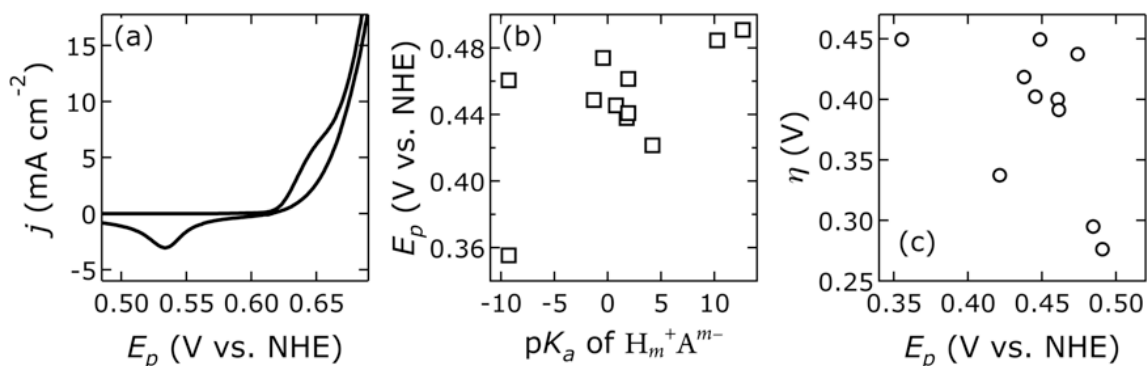


Figure 3.20. Magnified pre-water-oxidation-wave region of a representative cyclic voltammogram of [NiFe]-LDH nanosheets (a). Central polarization potential E_p of the reduction wave of [NiFe]-LDH nanosheets with different interlayer anions, collected in virtually carbonate-free electrolyte, as a function of anion basicity (b), and overpotential η as a function of E_p (c).

In addition, we investigated if the measured overpotentials depended on the intrasheet [NiFe](OH)₂ structure. To this end, we took IR spectra of our [NiFe]-(NO₃⁻)-LDH nanosheets that had been soaked in different pH aqueous KOH solutions and analyzed lines, which are characteristic for OH-deformations; the broad bands centered around 500 cm⁻¹ are Ni-O lattice modes⁵ (Figure 3.21 left). The ratios of two such lines as a function of solution pH showed sigmoid behavior with a midpoint of approximately 12 (Figure 3.21 right).

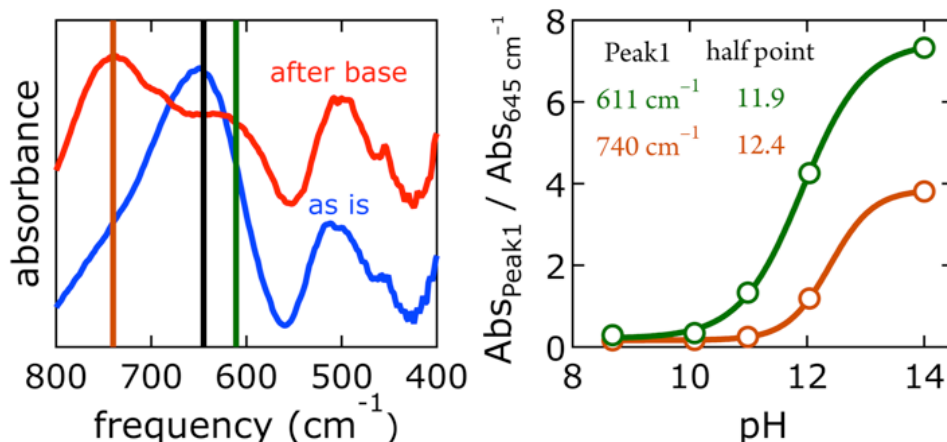


Figure 3.21. Left: IR spectra of [NiFe]-(NO₃)⁻-LDH nanosheets as synthesized (as is) and after suspension in 1.0 M aqueous KOH in ambient air (after base). The vertical lines indicate the peaks that were analyzed. Right: Titration curves as a function of solution pH.

We emphasize that we did not find that catalytic activity was a function of Ni^{3+/2+} prewave position,⁵⁸ indicating that the Ni^{3+/2+} couple is not the rate-determining step for water oxidation. Likewise, measured overpotentials did not depend on the slab [NiFe](OH)₂ structure, as evidenced by analysis of the IR spectra; intensities of characteristic OH-deformation modes as a function of soaking solution pH showed sigmoidal behavior with a midpoint of approximately 12, whereas overpotentials vs. p*K*_a values from anion-conjugate-acid data had a midpoint of 3.4 ± 0.7, indicating that intrasheet structural changes were unrelated to observed activities.

Perhaps surprisingly, measured overpotentials also did not depend on the basal spacings. In Figure 3.22, overpotentials of [NiFe]-LDH materials with different interlayer anions, collected in virtually carbonate-free electrolyte (glove box), are plotted as a function of the materials' basal spacings. Layer-to-layer spacings would only matter if reactants and products had to diffuse through the interlamellar galleries for redox reactions mediated by (central) intrasheet species. Clearly, this is not the case for our materials.

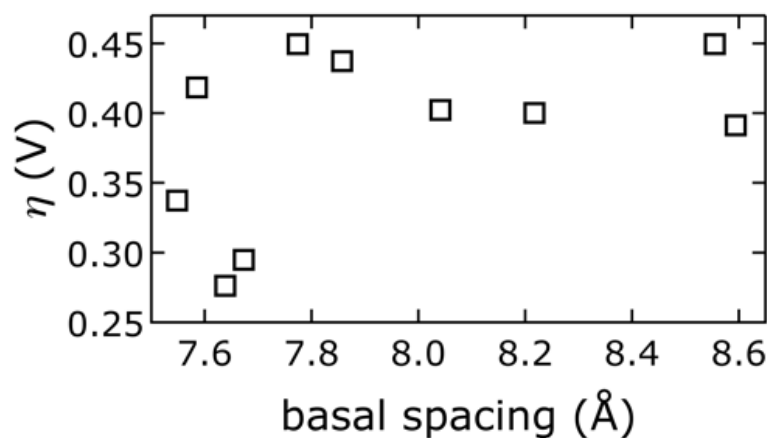


Figure 3.22. Observed overpotentials η at 10 min from chronopotentiometry data collected in virtually carbonate-free electrolyte (glove box) as a function of the basal spacing of [NiFe]-LDH materials with different interlayer anions.

3.4.3. Density functional theory calculations

We recently reported two distinct N 1s signals in the XPS data of PLAL-synthesized [NiFe]-(NO₃⁻)-LDH precatalysts.²⁰ One peak was centered at 407.3 eV, attributable to nitrate,⁴⁷ and the other at 405.1 eV, which we tentatively ascribed to nitrate or nitrite in an unusual chemical environment. Curiously, the turnover frequency of [NiFe]-(NO₃⁻)-LDH precatalysts with different Ni/Fe ratios depended on the relative proportion of the two XPS peaks.²⁰

We performed DFT calculations on model LDH clusters, [Ni₉Fe₁(OH)₂₀(NO_{2 or 3})], to obtain information about the previously unassigned N 1s XPS signal at 405.1 eV. We wanted to find out if binding nitrate or nitrite to the [NiFe]-LDH nanosheets in various positions and binding motifs could explain the observed N 1s binding energy (BE) of 405.1 eV. This BE would require either (i) a *lowering* of the N 1s BE of nitrate by 2.2 eV or (ii) an *increase* of the N 1s BE of nitrite by 1.6 eV. We calculated N 1s core level shifts relative to a nitrate anion, which was bound by a hydrogen bridge to the top-side of the cluster. Technical details concerning the calculation of the N 1s core level binding energies and the choice of the cluster models are described above.

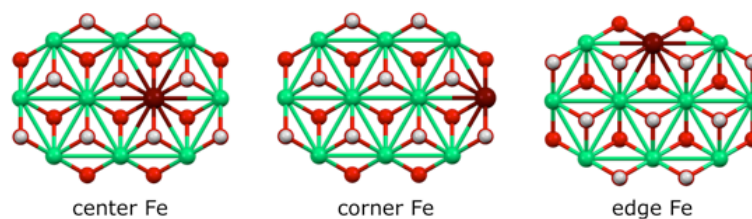


Figure 3.23. Fe sites in the basic $[\text{Ni}_9\text{Fe}_1(\text{OH})_{18}]^{3+}$ cluster fragment.
Colors: Ni green, Fe maroon, O red, H white.

We assessed the binding of nitrate and nitrite anions to different Fe sites within our prolate model clusters (central, edge at the rim along the long axis, and corner at the short-axis rim, Figure 3.23).

We also investigated different anion binding motifs: nitrate binding via one of its O atoms, nitrite binding by both O and N atom coordination (Figure 3.24).

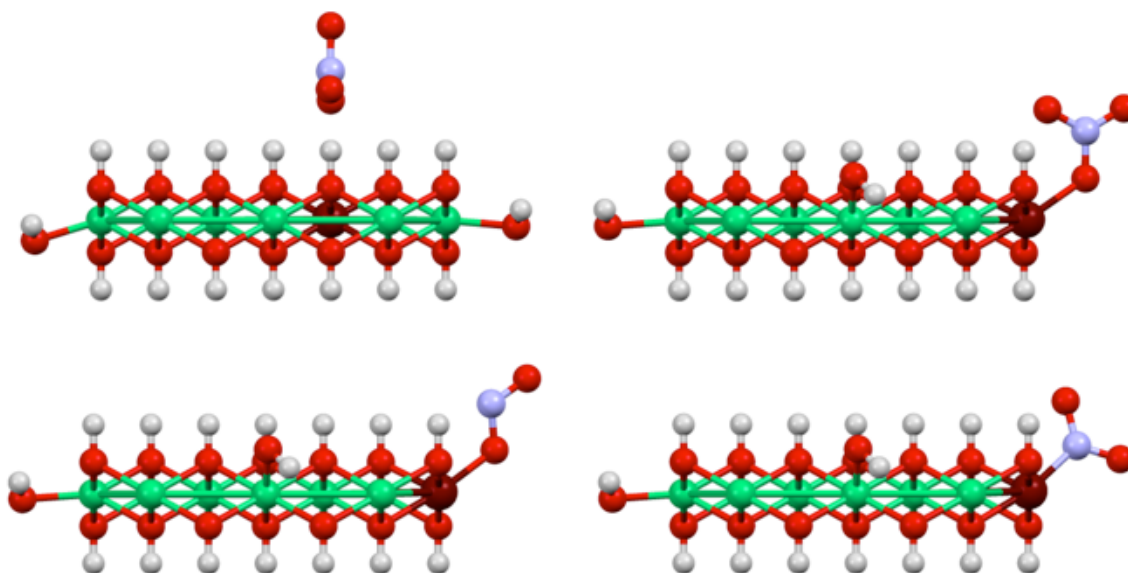


Figure 3.24. Illustration of the basic anion coordination motifs of NO_3^- (top) and NO_2^- (bottom) to $[\text{Ni}_9\text{Fe}_1(\text{OH})_{20}]$ clusters. Only coordination to corner sites of the clusters are shown here, other sites were also investigated (Figure 3.23). The top left structure shows the reference for the calculation of core level shift from core level binding energies. Colors: Ni green, Fe maroon, N blue, O red, H white.

The experimentally observed N 1s XPS peak at 405.1 eV corresponds to a core level shift of -2.2 eV with respect to the electron binding energy of pristine nitrate at 407.4 eV.⁴⁸ Calculations of nitrate binding to the clusters yielded core level shifts that were inconsistent with the XPS signal at 405.1 eV (Figure 3.25). However, N-coordination of nitrite to edge-site Fe resulted in a core level shift of -2.1 eV, which is in very close agreement with the experimentally observed shift. Other nitrite binding motifs were not in accord with the experimental XPS data. We note that formation of nitrite was possible during our PLAL from nitrate-containing ablation solutions, as evidenced by the fact that PLAL-made [NiFe]-(SO₄²⁻)-LDH exhibited an N 1s peak at 403.5 eV, attributable to nitrite (see above).⁴⁸

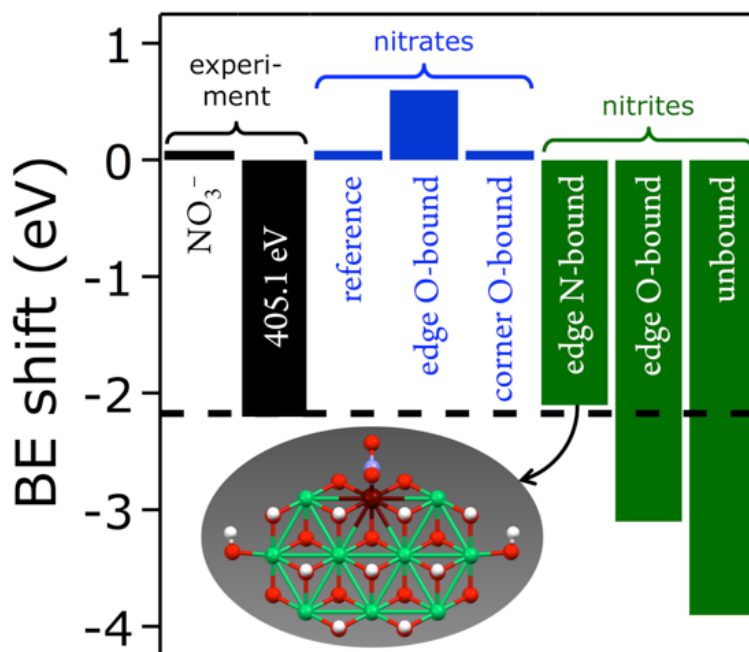


Figure 3.25. Measured (black) and calculated XPS binding energy (BE) shifts (is-CLS) for differently bound nitrates (blue) and nitrites (green) with a calculated structure that is consistent with the feature at 405.1 eV. Atom colors: Ni green, Fe maroon, N blue, O red, H white.

Assignment of the experimentally observed 405.1 eV N 1s peak of the [NiFe]-(NO₃⁻)-LDH nanosheet precatalyst to nitrite bound by its N-atom to edge-site Fe suggested

that this XPS signal provided a means to quantify Fe edge sites. It also rationalized why we had previously observed higher catalytic turnover frequencies as the relative proportion of the 405.1 eV peak with respect to that at 407.3 eV increased.²⁰ Therefore, we conclude that edge-site Fe plays a major role in water oxidation catalyzed by our PLAL-synthesized [NiFe]-LDH nanosheets. Our calculations are consistent with our observation that the overpotentials of [NiFe]-LDH materials with different interlayer anions did not correlate with basal spacings.

3.5. Conclusions

We synthesized a series of [NiFe]-LDH nanosheets with various intercalated anions, both directly by PLAL and by anion metathesis. We found that their water oxidation activity correlated with the pK_a of the conjugate acid of the interlayer anions and propose that the anions' Brønsted or Lewis basicity plays a role in the water oxidation mechanism. Our nanocatalysts were regenerated and most active in alkaline electrolyte in ambient air, as carbonate rapidly replaced other interlayer anions. Finally, our DFT calculations suggest that a previously unassigned N 1s species in the precatalyst, which correlated with higher water oxidation activity,²⁰ is consistent with nitrite bound by its N-atom to edge-site iron. This finding implies that iron sites at the edges of our [NiFe]-LDH nanosheets are active in water oxidation catalysis.

3.6. References and Notes

- (1) H. B. Gray, *Nature Chem.*, 2009, **1**, 7-7.
- (2) N. S. Lewis and D. G. Nocera, *Proc. Natl. Acad. Sci. U. S. A.*, 2006, **103**, 15729-15735.

- (3) Y. Lee, J. H. Choi, H. J. Jeon, K. M. Choi, J. W. Lee and J. K. Kang, *Energy Environ. Sci.*, 2011, **4**, 914-920.
- (4) M. Gong, Y. Li, H. Wang, Y. Liang, J. Z. Wu, J. Zhou, J. Wang, T. Regier, F. Wei and H. Dai, *J. Am. Chem. Soc.*, 2013, **135**, 8452-8455.
- (5) B. Li, Y. Zhao, S. Zhang, W. Gao and M. Wei, *ACS Appl. Mater. Interfaces*, 2013, **5**, 10233-10239.
- (6) Y. Zhang, B. Cui, C. Zhao, H. Lin and J. Li, *Phys. Chem. Chem. Phys.*, 2013, **15**, 7363-7369.
- (7) X. Zou, A. Goswami and T. Asefa, *J. Am. Chem. Soc.*, 2013, **135**, 17242-17245.
- (8) S. J. Kim, Y. Lee, D. K. Lee, J. W. Lee and J. K. Kang, *J. Mater. Chem. A*, 2014, **2**, 4136-4139.
- (9) Y. Li, L. Zhang, X. Xiang, D. Yan and F. Li, *J. Mater. Chem. A*, 2014, **2**, 13250-13258.
- (10) D. Tang, Y. Han, W. Ji, S. Qiao, X. Zhou, R. Liu, X. Han, H. Huang, Y. Liu and Z. Kang, *Dalton Trans.*, 2014, **43**, 15119-15125.
- (11) O. Diaz-Morales, I. Ledezma-Yanez, M. T. M. Koper and F. Calle-Vallejo, *ACS Catal.*, 2015, **5**, 5380-5387.
- (12) I. J. Godwin and M. E. G. Lyons, *Electrochem. Commun.*, 2013, **32**, 39-42.

- (13) M. Gong, Y. Li, H. Wang, Y. Liang, J. Z. Wu, J. Zhou, J. Wang, T. Regier, F. Wei and H. Dai, *J. Am. Chem. Soc.*, 2013, **135**, 8452-8455.
- (14) M. Gao, W. Sheng, Z. Zhuang, Q. Fang, S. Gu, J. Jiang and Y. Yan, *J. Am. Chem. Soc.*, 2014, **136**, 7077-7084.
- (15) F. Song and X. Hu, *Nat. Commun.*, 2014, **5**, 4477-4486.
- (16) L. Trotochaud, S. L. Young, J. K. Ranney and S. W. Boettcher, *J. Am. Chem. Soc.*, 2014, **136**, 6744-6753.
- (17) Y. Zhao, B. Li, Q. Wang, W. Gao, C. J. Wang, M. Wei, D. G. Evans, X. Duan and D. O'Hare, *Chem. Sci.*, 2014, **5**, 951-958.
- (18) C. G. Morales-Guio, M. T. Mayer, A. Yella, S. D. Tilley, M. Grätzel and X. Hu, *J. Am. Chem. Soc.*, 2015, **137**, 9927-9936.
- (19) M. W. Louie and A. T. Bell, *J. Am. Chem. Soc.*, 2013, **135**, 12329-12337.
- (20) B. M. Hunter, J. D. Blakemore, M. Deimund, H. B. Gray, J. R. Winkler and A. M. Müller, *J. Am. Chem. Soc.*, 2014, **136**, 13118-13121.
- (21) M. S. Burke, L. J. Enman, A. S. Batchellor, S. Zou and S. W. Boettcher, *Chem. Mater.*, 2015, **27**, 7549-7558.
- (22) M. S. Burke, M. G. Kast, L. Trotochaud, A. M. Smith and S. W. Boettcher, *J. Am. Chem. Soc.*, 2015, **137**, 3638-3648.

- (23) X. Duan and D. G. Evans, *Layered double hydroxides*, Springer Science & Business Media, 2006.
- (24) S. Miyata, *Clays Clay Miner.*, 1983, **31**, 305-311.
- (25) D. G. Evans and R. C. Slade, *Struct. Bond.*, 2006, **119**, 1-87.
- (26) J. D. Blakemore, H. B. Gray, J. R. Winkler and A. M. Müller, *ACS Catal.*, 2013, **3**, 2497-2500.
- (27) T. L. Barr and S. Seal, *J. Vac. Sci. Technol. A*, 1995, **13**, 1239-1246.
- (28) D. A. Shirley, *Phys. Rev. B*, 1972, **5**, 4709-4714.
- (29) P. Scherrer, *Nachr. Ges. Wiss. Göttingen*, 1918, **26**, 98-100.
- (30) J. I. Langford and A. J. C. Wilson, *J. Appl. Crystallogr.*, 1978, **11**, 102-113.
- (31) W. H. Bragg and W. L. Bragg, *Proc R. Soc. Lond. A*, 1913, **88**, 428-438.
- (32) J. E. S. Han and T. Y. Chao, *Ind. Eng. Chem. Anal. Ed.*, 1932, **4**, 229-232.
- (33) R. Ahlrichs, F. Furche, C. Hättig, W. M. Klopper, M. Sierka and F. Weigend, *Turbomole program package, version 6.6*, Karlsruhe, Germany, since 1989 (<http://www.turbomole.com>).
- (34) C. Adamo and V. Barone, *J. Chem. Phys.*, 1999, **110**, 6158-6170.
- (35) M. Ernzerhof and G. E. Scuseria, *J. Chem. Phys.*, 1999, **110**, 5029-5036.

- (36) J. P. Perdew, M. Ernzerhof and K. Burke, *J. Chem. Phys.*, 1996, **105**, 9982-9985.
- (37) F. Weigend and R. Ahlrichs, *Phys. Chem. Chem. Phys.*, 2005, **7**, 3297-3305.
- (38) A. Klamt and G. Schüürmann, *J. Chem Soc., Perkin Trans. 2*, 1993, 799.
- (39) A. Schäfer, A. Klamt, D. Sattel, J. C. Lohrenz and F. Eckert, *Phys. Chem. Chem. Phys.*, 2000, **2**, 2187-2193.
- (40) J. C. Slater, *Adv. Quantum Chem.*, 1972, **6**, 92.
- (41) N. N. Greenwood and A. Earnshaw, *Chemistry of the Elements*, 1984.
- (42) R. N. King, *ESCA Binding Energy Chart*, Surface Science Instruments, Mountain View, CA.
- (43) A. N. Mansour and C. A. Melendres, *Surf. Sci. Spectra*, 1994, **3**, 247-254.
- (44) *NIST X-ray Photoelectron Spectroscopy Database*, X-ray Photoelectron Spectroscopy Database 20, Version 4.1 (National Institute of Standards and Technology, Gaithersburg, 2012); <http://srdata.nist.gov/xps/>.
- (45) M. C. Biesinger, B. P. Payne, L. W. M. Lau, A. Gerson and R. S. C. Smart, *Surf. Interface Anal.*, 2009, **41**, 324-332.
- (46) W. Temesghen and P. Sherwood, *Anal. Bioanal. Chem.*, 2002, **373**, 601-608.

- (47) C. E. Nanayakkara, P. M. Jayaweera, G. Rubasinghege, J. Baltrusaitis and V. H. Grassian, *J. Phys. Chem. A*, 2013, **118**, 158-166.
- (48) J. Baltrusaitis, P. M. Jayaweera and V. H. Grassian, *Phys. Chem. Chem. Phys.*, 2009, **11**, 8295-8305.
- (49) C. Vaysse, L. Guerlou-Demourgues and C. Delmas, *Inorg. Chem.*, 2002, **41**, 6905-6913.
- (50) T. S. Stanimirova, G. Kirov and E. Dinolova, *J. Mater. Sci. Lett.*, 2001, **20**, 453-455.
- (51) S. Carlino, *Solid State Ionics*, 1997, **98**, 73-84.
- (52) D. R. Lide, *CRC Handbook of Chemistry and Physics*, CRC Press, Boca Raton, FL, USA, 72nd edn., 1991.
- (53) V. Rives, *Mater. Chem. Phys.*, 2002, **75**, 19-25.
- (54) T. Stanimirova, N. Piperov, N. Petrova and G. Kirov, *Clay Miner.*, 2004, **39**, 177-191.
- (55) F. A. Miller and C. H. Wilkins, *Anal. Chem.*, 1952, **24**, 1253-1294.
- (56) W. L. F. Armarego and D. D. Perrin, *Purification of Laboratory Chemicals*, Butterworth-Heinemann, Oxford, UK, 4th edn., 1987.
- (57) J. R. Winkler and H. B. Gray, *Struct. Bond.*, 2012, **142**, 17-28.

- (58) The prewaves of nickel-iron double hydroxide cyclic voltammograms have previously been assigned to the $\text{Ni}^{3+/2+}$ redox couple (Trotochaud, L.; Young, S. L.; Ranney, J. K.; Boettcher, S. W. *J. Am. Chem. Soc.* 2014, **136**, 6744-6753).
- (59) J. Moir and N. Wood, *CMLS, Cell. Mol. Life Sci.*, 2001, **58**, 215-224.
- (60) T. Sudakova and V. Krasnoshchekov, *Zh. Neorg. Khim.*, 1978, **23**, 1506-1508.
- (61) W. E. Dasent, *Inorganic energetics: an introduction*, Cambridge University Press, Cambridge, UK, 1982. Chapter 5.
- (62) D. R. Lide, *CRC Handbook of Chemistry and Physics*, CRC Press, Boca Raton, FL, USA, 72nd edn., 1991.